

# FIXCOLOR 4/16

## Coloured-cement mortar, for sealing 4 mm - 16 mm joints.

### Preparing the joints:

- ◆ The joints must be clean and dust-free.
- ◆ The ambient temperature must be between +5°C and +35°C.
- ◆ Allow 24 hours between laying the tiles and grouting.
- ◆ In summer, when it is very hot, the joints must be wetted with water before beginning to grout.

### Preparing the mixture:

- ◆ Mix 5.3 l of water with 25 kg of **FIXCOLOR 4/16**, or mix 1.0 l of water with 5 kg of **FIXCOLOR 4/16**.
- ◆ Mix with an electric drill and mixing attachment.
- ◆ Mixing too quickly will cause bubbles to form in the surface of the joints.
- ◆ Mixing too slowly or by hand will cause the pigment which colours the paste to be badly distributed and the joint may discolour in the future.
- ◆ Mix well and allow the mixture to stand for 2 minutes.
- ◆ Then re-mix with the electric mixer.
- ◆ The paste is now ready for application.



### WARNING

**FIXCOLOR 4/16** must not be used:

- ◆ For joints resistant to acids (use **CERPOXI**).
- ◆ For dilation joints (use **SELLALASTIC**).
- ◆ Mixed with dirty water or lime (colour differences would appear in the joints).



Sealing joints in swimming-pool beaches.



Use the rubber **FIX-SPATULA**.

### Applying the mix:

- ◆ Fill the joints with the **FIX-SPATULA**.
- ◆ Make diagonal passes on the joints so that the **FIX-SPATULA** does not collide with the sides of the tiles.
- ◆ As you grout, all the excess is collected by the **FIX-SPATULA**.

**Cleaning:**

- ◆ After 30 minutes, clean the tiles with the **FIX-SPONGE** or the **FIX-LLANA FOR CLEANING**, slightly dampened with water.
- ◆ If you use the **FIX-SPONGE**, it must NOT be wetted with water: it must only be dampened.
- ◆ The tools may be cleaned in the special **FIX-BUCKET**.
- ◆ Clean only once: further cleaning will only succeed in weakening the colour and the joint's resistance.


 Use the **FIX-BUCKET** and the **FIX-SPONGE**.

**Final cleaning:**

- ◆ The next day, remove the film of colour with a dry cloth.
- ◆ Nothing else need be used: neither water nor a scourer...only a dry cloth or sponge.



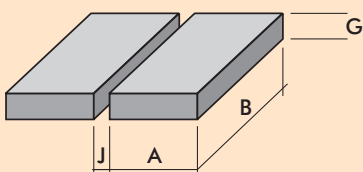
Carry out a dry cleaning.

**Final cleaning on rough tiles:**

- ◆ 7 days after grouting, remove the excess with 1 part **GRESNET** acid and 10 parts water.

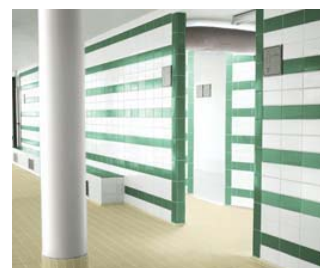

 If necessary, clean with **GRESNET**.

**CONSUMPTION:** the following formula is used to find out the consumption:



$$\frac{A + B}{A \times B} \times J \times G \times 1,6 = \text{kg./m}^2$$

A, B, J, G in mm.



Inexpensive, long- lasting grouting.

